

PROCEEDINGS

One Hundred First Annual Meeting

of the

AMERICAN WOOD-PRESERVERS' ASSOCIATION

Royal Sonesta Hotel
New Orleans, Louisiana
May 15-17, 2005

VOLUME 101

**AMERICAN WOOD-PRESERVERS' ASSOCIATION
P.O. BOX 361784 BIRMINGHAM, ALABAMA 35236-1784 USA**

Bending Properties of Southern Pine Treated With Waterborne Copper Naphthenate

H. M. Barnes, Professor
M. Maupin, Research Associate I
G. B. Lindsey, Research Associate II
Forest Products Laboratory
Mississippi State University

This paper was accepted for publication in the 2005 AWWA Proceedings as a refereed paper subject to a peer review process as determined by AWWA Committee S-2 Wood Preservation Research. It was approved for publication as Journal Article No. FP-347, Forest & Wildlife Research Center, Mississippi State University.

Abstract: Southern pine treated with a waterborne copper naphthenate (CuN) preservative at 0.04, 0.075, and 0.13 pcf Cu (as metal) was tested in static bending. Comparison was with control samples treated with water only and samples treated with CCA type C at 0.1, 0.2, and 0.4 pcf (total oxide). Comparison of the treatments showed no deleterious effect of treatment on most bending properties for either CuN- or CCA-treated wood at the retentions tested. Work-to-maximum load at the higher retentions for CuN were the only calculated values lower than the controls. The critical design values modulus of rupture and modulus of elasticity were the same as control values as were fiber stress and longitudinal shear.

Keywords: waterborne copper naphthenate, southern pine, bending strength, stiffness, work, CCA

Introduction: For a wood preservative or fire retardant to have utility, it must not have a deleterious effect on wood properties. It is a requirement for all systems standardized by AWWA. Therefore, all data packages presented for consideration must include the effects on mechanical properties. Many studies have been conducted on the effect of various treatments on the mechanical properties of wood. Research by Winandy and others (Winandy et al. 1992; Winandy and Barnes 1991; Barnes et al. 1990; Barnes and Winandy 1989) resulted in drying temperature limitations for CCA-treated wood and for design factors for fire retardant-treated wood (Barnes 1993, 1994; Winandy et al. 1991; Winandy, Ross and LeVan 1991). Other work has shown ACQ and other treatments not to cause significant reductions in mechanical properties (Barnes, et al. 1993; Barnes and Winandy 1986). This paper reports on the testing of southern pine treated with a new generation, waterborne copper naphthenate system.

Methods and Materials

Materials—All sapwood, defect-free southern pine samples were cut from commercial dimension stock. Samples were randomly assigned to seven treatment groups such that each group would have a similar density range, ring count, and earlywood/latewood ratio. Both CCA-type C and waterborne copper naphthenate (CuNWB) concentrates were used to prepare treating solutions by water dilution.

Treatment—All samples were treated using a full-cell cycle consisting of 30 minutes of vacuum at -88 kPa, introduction of treating solution under vacuum, increasing to 1035 kPa in five minutes and holding for one hour, venting to atmospheric pressure in five minutes, and removal of samples from the treating solution. Samples were weighed before treatment and after the wiping of excess solution following treatment in order to determine preservative retention by weight gain. Three CuNWB retentions (0.04, 0.075, 0.13 pcf Cu as metal) and three CCA type C retentions (0.1, 0.2, 0.4 pcf total oxide basis) were tested. Comparison was with untreated southern pine controls which had been treated with water only. Thirty samples at each retention level were treated. Samples were allowed to equilibrate at 75° F in a constant moisture content room before testing.

AMERICAN WOOD-PRESERVERS' ASSOCIATION

Testing and analysis—Samples were tested in static bending with center-point loading according to D143 (ASTM International 2004). Specimen size was one-in x one-in in cross-section x 16-in long with a 14-in span. A machine speed of 0.109 in/min was employed. Moisture content and specific gravity were determined on small samples cut from near the break of the bending samples. Modulus of elasticity (E), modulus of rupture (R), work-to-maximum load (W_{ml}), work-to-proportional limit (elastic resilience, W_{pl}), fiber stress at proportional limit (FS_{pl}), and greatest calculated longitudinal shear were computed for each sample. The data were analyzed using covariate analysis and mean separation techniques (SAS Institute 2001).

Results and Discussion

A cumulative distribution curve for modulus of rupture values is shown in Figure 1. This family of curves is typical of the distribution in property values for the samples in this study and indicate no deleterious impact of treatment on modulus of rupture. Descriptive statistics for the various treatment groups are given in Table 1. Note that these are mean values and differ from the least square means presented in the graphs and in Table 2. The analysis of covariance showed specific gravity to be a significant covariate in the statistical analysis.

Least square means for modulus of rupture, modulus of elasticity, and fiber stress at proportional limit are shown in Figure 2. None of these mean values were significantly lower than the control values. Modulus of rupture averaged 93-104% of the control value with samples treated with CCA slightly higher and CuN slightly lower than the controls. For modulus of elasticity, CCA values averaged 9% higher and CuN values 4% higher than controls. CuN treatments averaged 1% higher and CCA treatments 4% higher than controls in fiber stress.

Work values are compared in Figure 3. Work-to-proportional limit values ranged from 94% to 107% of the control values depending on treatment but were not significantly different from control values. Only with work-to-maximum load were significant decreases found compared to control values. In this instance, CuN treatment averaged 83% of the control value while CCA treatment averaged 93% of the control. A similar result was found with ACQ-treated 2 x 6s reported in 1993 (Barnes *et al.* 1993) in which the treated material averaged 68% of the control value.

Shear values are shown in Figure 4. No significant differences due to treatment were noted. Treated samples averaged 94% to 104% of control values.

Summary and Conclusions

The data obtained in this study would indicate that little to no deleterious effect on bending properties was seen with treatments using waterborne copper naphthenate. This result is similar to results obtained with other waterborne preservative systems. While no data are presented, it would seem prudent to restrict redrying of stock treated with waterborne copper naphthenate to the same 160° F limit applicable to other waterborne systems until a definitive redrying study can be done.

References

- ASTM International. 2004. ASTM D 143-94 (2000): Standard test methods for small clear specimens of timber. Annual Book of Standards 2004, Section 4 Construction, Vol. 04.10 Wood, ASTM International, West Conshohocken, PA, p. 25-58.
- Barnes, H. M. 1993. U. S. experience with flame retardants. *In*: Proceedings, 1993 Eurowood Oxford Fire Conference, Timber Research & Development Association, July 1-2, 1993, Mansfield College, Oxford University, Oxford, England, UK.
- Barnes, H. M. 1994. A historical perspective of fire retardants in the AWWPA. Appendix A, Report of Committee T-9 Fire Retardant Treated Commodities (J. E. Winandy, Chm.). Proceedings of the American Wood-Preservers' Association 90:413-433.
- Barnes, H. M.; Lyon, D. E.; Zahora, A.; Muisu, F. 1993. Strength properties of ACQ-treated southern pine lumber. Proceedings of the American Wood-Preservers' Association 89:51-60.
- Barnes, H. M. and J. E. Winandy. 1986. Effects of seasoning and preservatives on the properties of treated wood. Proceedings: American Wood-Preservers' Association 82:95-105.

AMERICAN WOOD-PRESERVERS' ASSOCIATION

- Barnes, H. M. and J. E. Winandy. 1989. Mechanical properties of CCA-treated southern pine after post-treatment kiln drying. International Research Group on Wood Preservation Document No. IRG/WP/3543, 11 pp.
- Barnes, H. M., J. E. Winandy, and P. H. Mitchell. 1990. Effect of initial and post-treatment drying temperatures on the bending properties of CCA-treated southern pine. *J. Inst. Wood Sci.* 11(6):222-230.
- SAS Institute Inc. 2001. SAS Proprietary Software, Release 8.2. The SAS Institute, Cary, NC.
- Winandy, J. E., and H. M. Barnes. 1991. Influence of initial kiln-drying temperature on CCA-treatment effects on strength. *Proceedings of the American Wood-Preservers' Association* 87:147-152.
- Winandy, J. E., H. M. Barnes, and P. H. Mitchell. 1992. Effect of CCA treatment and drying on tensile strength of lumber. *J. Materials in Civil Engineering* 4(3):240-251.
- Winandy, J. E.; LeVan, S. L.; Ross, R. J.; Hoffman, S. P.; McIntyre, C. R. 1991. Thermal degradation of fire-retardant-treated plywood: development of a test protocol. Research Paper FPL-RP-501, USDA Forest Service, Forest Products Laboratory, Madison, WI, 21 pp.
- Winandy, J. E.; Ross, R. J.; LeVan, S. L. 1991. Fire-retardant-treated wood: research at the Forest Products Laboratory. In: *Proceedings, 1991 International Timber Engineering Conference, Vol. 4, London, UK*, p. 4.69-4.74.

AMERICAN WOOD-PRESERVERS' ASSOCIATION

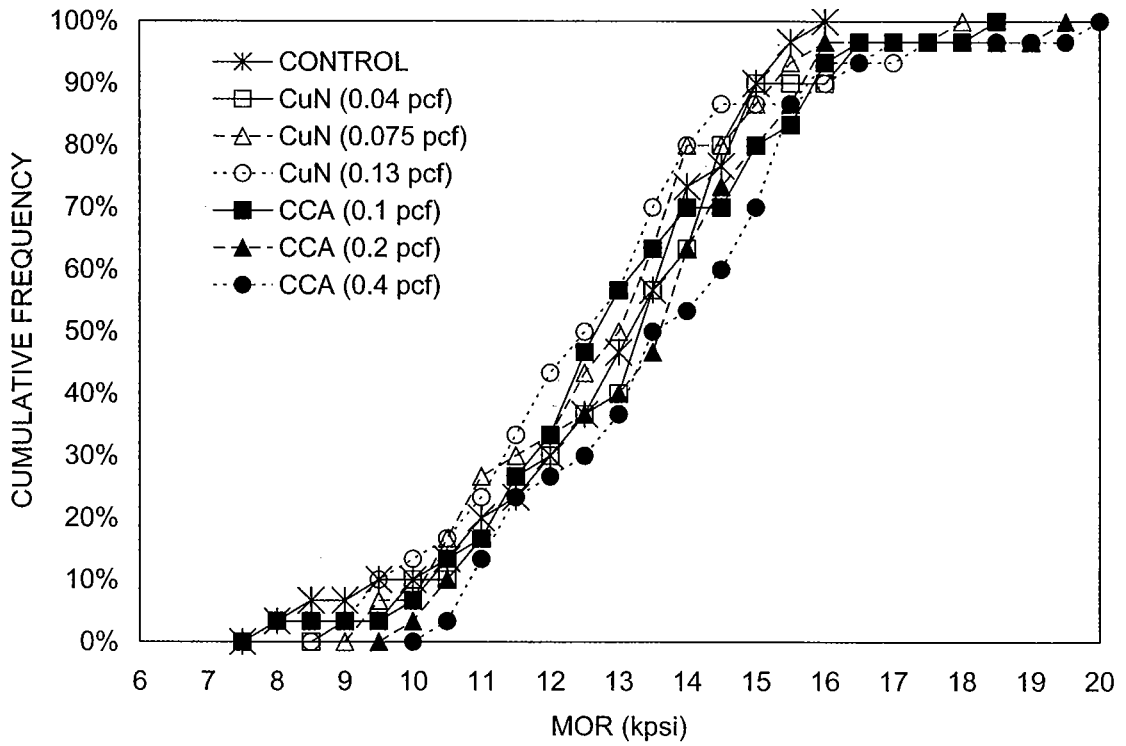


Figure 1. Cumulative frequency diagram of modulus of rupture (MOR) for the various treatment groups in this study.

AMERICAN WOOD-PRESERVERS' ASSOCIATION

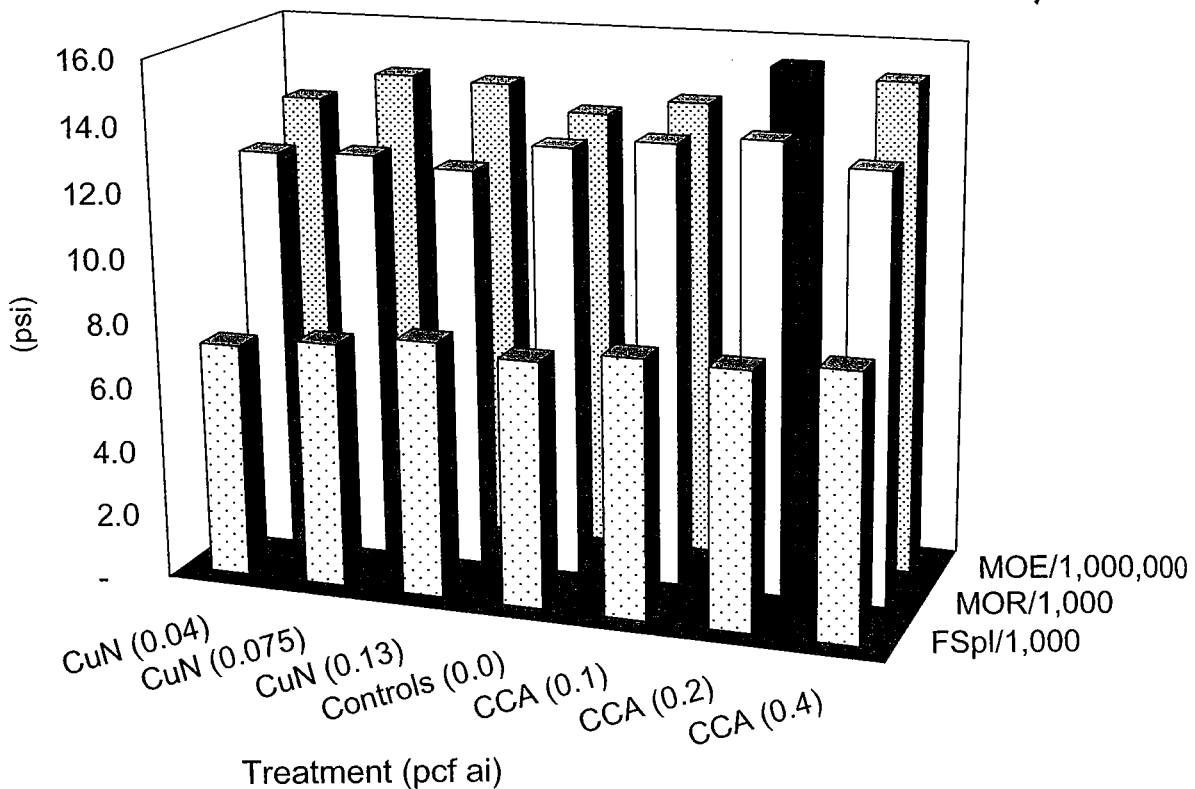


Figure 2. A comparison of least square means adjusted for specific gravity for modulus of rupture (MOR), modulus of elasticity (MOE), and fiber stress at proportional limit (FS_{pl}) by treatment (darkened bar indicates a mean value significantly different from the control).

AMERICAN WOOD-PRESERVERS' ASSOCIATION

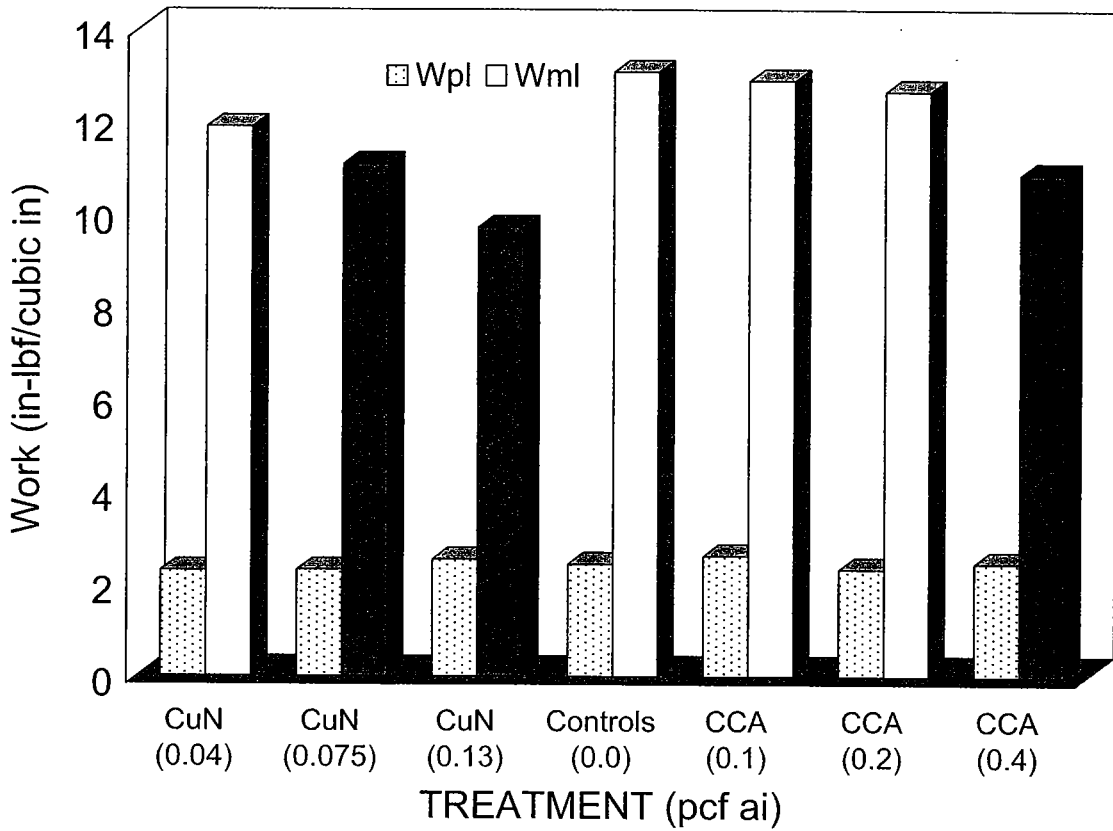


Figure 3. Least square means adjusted for specific gravity for work-to-proportional limit (W_{pl}) and work-to-maximum load (W_{ml}) by treatment (darkened bars indicate means significantly different from the control value).

AMERICAN WOOD-PRESERVERS' ASSOCIATION

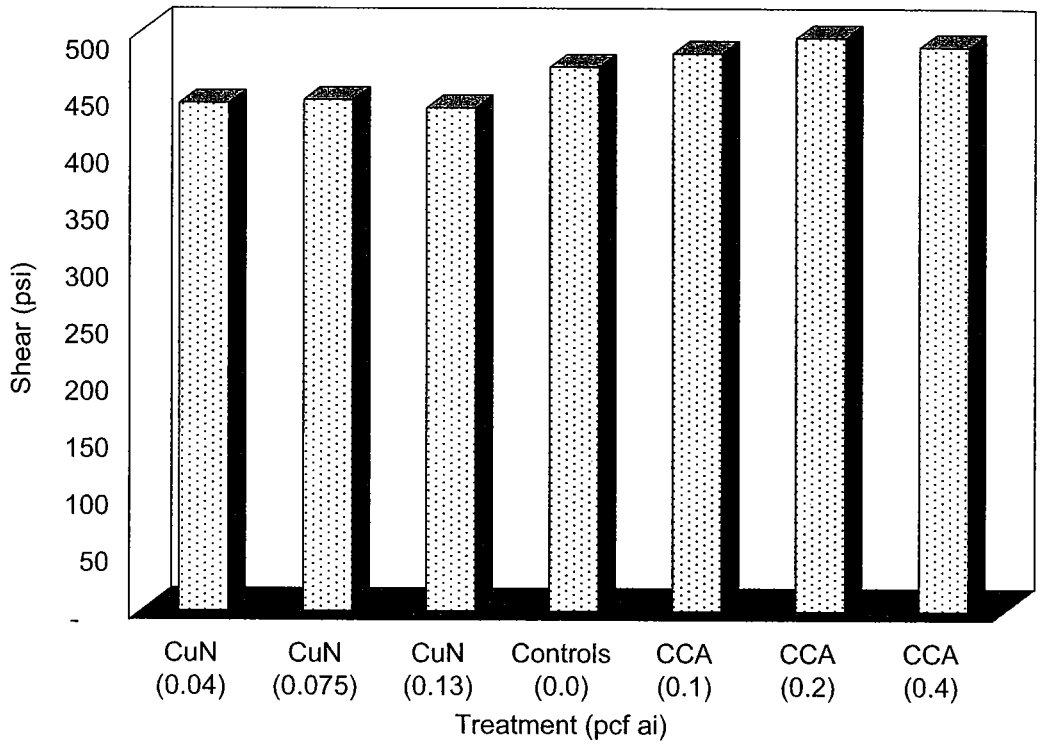


Figure 4. Least square means adjusted for specific gravity for greatest calculated longitudinal shear by treatment.

AMERICAN WOOD-PRESERVERS' ASSOCIATION

Table 1. Property values for treated specimens tested in static bending.

| Item | Treatment | Retention (pcf) | MOR (psi) | MOE (psi) | Work-to-max load (in-lbf/in ³) | Work-to-prop. Limit (in-lbf/in ³) | Fiber stress @ prop. Limit (psi) | Moisture content (%) | Specific gravity |
|------------------------------|-----------|-----------------|-----------|-----------|--|---|----------------------------------|----------------------|------------------|
| Mean | CONTROLS | 0.000 | 12,763 | 1,332,520 | 12.27 | 2.35 | 7,372 | 9.64 | 0.466 |
| Standard Deviation | | | 2,035 | 194,534 | 3.85 | 0.55 | 1,274 | 0.54 | 0.049 |
| Coefficient of Variation (%) | | | 16 | 15 | 31 | 23 | 17 | 6 | 11 |
| Median | | | 13,269 | 1,362,191 | 12.76 | 2.32 | 7,262 | 9.57 | 0.466 |
| Minimum | | | 7,965 | 944,600 | 4.09 | 1.42 | 5,034 | 8.80 | 0.380 |
| Maximum | | | 15,551 | 1,668,034 | 18.36 | 3.77 | 10,397 | 10.89 | 0.590 |
| Mean | CCA-C | 0.103 | 12,965 | 1,369,514 | 11.97 | 2.51 | 7,659 | 9.98 | 0.460 |
| Standard Deviation | | | 2,154 | 247,298 | 4.56 | 0.74 | 1,794 | 0.42 | 0.046 |
| Coefficient of Variation (%) | | | 17 | 18 | 38 | 30 | 23 | 4 | 10 |
| Median | | | 12,703 | 1,359,321 | 10.89 | 2.41 | 7,533 | 9.93 | 0.453 |
| Minimum | | | 7,972 | 945,138 | 3.50 | 0.14 | 1,511 | 9.08 | 0.384 |
| Maximum | | | 18,056 | 1,943,981 | 21.33 | 4.35 | 11,070 | 10.76 | 0.592 |
| Mean | CCA-C | 0.206 | 13,271 | 1,488,975 | 11.93 | 2.22 | 7,569 | 10.52 | 0.458 |
| Standard Deviation | | | 2,112 | 266,532 | 3.69 | 0.54 | 1,447 | 0.42 | 0.037 |
| Coefficient of Variation (%) | | | 16 | 18 | 31 | 24 | 19 | 4 | 8 |
| Median | | | 13,518 | 1,510,280 | 11.75 | 2.06 | 7,451 | 10.49 | 0.453 |
| Minimum | | | 9,702 | 1,000,367 | 4.32 | 1.34 | 5,420 | 9.89 | 0.393 |
| Maximum | | | 19,174 | 2,223,369 | 17.18 | 3.97 | 12,454 | 11.45 | 0.533 |
| Mean | CCA-C | 0.418 | 13,656 | 1,505,041 | 12.40 | 2.53 | 8,106 | 13.16 | 0.481 |
| Standard Deviation | | | 2,114 | 271,040 | 3.68 | 0.59 | 1,567 | 1.77 | 0.063 |
| Coefficient of Variation (%) | | | 15 | 18 | 30 | 23 | 19 | 13 | 13 |
| Median | | | 13,522 | 1,494,216 | 11.83 | 2.47 | 7,948 | 13.79 | 0.466 |
| Minimum | | | 10,089 | 1,100,517 | 6.25 | 1.62 | 5,576 | 9.56 | 0.358 |
| Maximum | | | 19,649 | 2,440,287 | 21.78 | 4.42 | 13,559 | 15.97 | 0.609 |

AMERICAN WOOD-PRESERVERS' ASSOCIATION

Table 1. Property values for treated specimens tested in static bending.

| Item | Treatment | Retention (pcf) | MOR (psi) | MOE (psi) | Work-to-max load (in-lbf/in ³) | Work-to-prop. Limit (in-lbf/in ³) | Fiber stress @ prop. Limit (psi) | Moisture content (%) | Specific gravity |
|------------------------------|-----------|-----------------|-----------|-----------|--|---|----------------------------------|----------------------|------------------|
| Mean | CuN | 0.041 | 13,123 | 1,426,877 | 12.63 | 2.39 | 7,657 | 8.36 | 0.515 |
| Standard Deviation | | 0.003 | 2,119 | 263,876 | 4.03 | 0.62 | 1,516 | 0.74 | 0.054 |
| Coefficient of Variation (%) | | 7 | 16 | 18 | 32 | 26 | 20 | 9 | 10 |
| Median | | 0.041 | 13,406 | 1,430,013 | 12.18 | 2.32 | 7,560 | 8.31 | 0.517 |
| Minimum | 0.034 | 8,755 | 913,944 | 5.90 | 1.40 | 5,032 | 5.91 | 0.419 | |
| Maximum | 0.045 | 18,207 | 1,945,271 | 21.00 | 3.73 | 11,169 | 10.31 | 0.604 | |
| Mean | CuN | 0.076 | 12,751 | 1,475,313 | 11.11 | 2.32 | 7,708 | 8.79 | 0.495 |
| Standard Deviation | | 0.005 | 2,036 | 202,388 | 4.25 | 0.47 | 1,214 | 0.72 | 0.054 |
| Coefficient of Variation (%) | | 7 | 16 | 14 | 38 | 20 | 16 | 8 | 11 |
| Median | | 0.077 | 12,945 | 1,506,045 | 10.73 | 2.26 | 7,662 | 8.84 | 0.490 |
| Minimum | 0.065 | 9,119 | 1,184,802 | 4.53 | 1.61 | 5,780 | 6.44 | 0.402 | |
| Maximum | 0.084 | 17,806 | 2,050,811 | 21.91 | 3.46 | 11,211 | 10.16 | 0.587 | |
| Mean | CuN | 0.136 | 12,629 | 1,479,288 | 9.94 | 2.58 | 8,131 | 8.49 | 0.501 |
| Standard Deviation | | 0.008 | 2,350 | 247,365 | 3.63 | 0.58 | 1,487 | 1.16 | 0.052 |
| Coefficient of Variation (%) | | 6 | 19 | 17 | 37 | 23 | 18 | 14 | 10 |
| Median | | 0.138 | 12,499 | 1,497,739 | 9.65 | 2.51 | 7,793 | 8.43 | 0.502 |
| Minimum | 0.118 | 8,617 | 1,031,244 | 3.89 | 1.60 | 5,829 | 5.88 | 0.389 | |
| Maximum | 0.147 | 18,956 | 2,225,416 | 18.08 | 4.30 | 12,876 | 13.43 | 0.600 | |

Table 2. Least square mean comparisons.

| Treatment | Retention (pcf ai) | MOR (psi) | MOE (psi) | FS _{pl} (psi) | W _{pl} (in-lbf/in ³) | W _{ml} (in-lbf/in ³) | Shear (psi) |
|-----------|-----------------------|--------------|--------------|---------------------------|--|--|----------------|
| CCA-C | 0.103 | 13,536 | 1,413,209 | 7,935 | 2.61 | 12.90 | 489.2 |
| CCA-C | 0.206 | 13,792 | *1,535,571 | 7,838 | 2.32 | 12.67 | 499.7 |
| CCA-C | 0.418 | 13,115 | 1,506,188 | 7,957 | 2.45 | *10.88 | 475.3 |
| CONTROL | 0.000 | 13,228 | 1,364,161 | 7,587 | 2.43 | 13.09 | 479.4 |
| CuN | 0.041 | 12,517 | 1,363,814 | 7,320 | 2.28 | 11.89 | 455.0 |
| CuN | 0.076 | 12,622 | 1,452,635 | 7,611 | 2.30 | *11.09 | 455.8 |
| CuN | 0.136 | 12,349 | 1,441,950 | 7,954 | 2.53 | *9.72 | 450.4 |

* indicates values that are significantly different from the control value at p = 0.05.